

10/14 Concassé

Péetrographie : RHYOLITE
Elaboration : Concassé

Partie normative

Valeurs spécifiées sur lesquelles le producteur s'engage

Classe granulaire

Norme

Code

10 14

Norme NF P 18-545 Article 8 - EN 13043


Bnc II Ang1 C100/0

	d/2		d		D		1.4D		2D		f	FI	MBF	LA	MDE	PSV
	0.063	4	5	6.3	8	10	12.5	14	16	20						
Etendue e						10		10								
V.S.S.+U	1.3		6			22		98				1.3				
V.S.S.	1.0		5			17		93				1.0	20	10.0	20	15
V.S.I.	0.0		0			7		83		98	100	0.0				50
V.S.I.-U	0.0		0			2		78		97		0.0				

Partie informative

Résultats de production

	du 15/02/23 au 13/12/23													du 01/01/22 au 30/12/23			
	0.063	4	5	6.3	8	10	12.5	14	16	20	28	f	FI	MBF	LA	MDE	PSV
Maximum	0.8	2	2	3	7	16	67	92	100	100	100	0.8	13	7.0	14	8	56
Xf+1.25xEcart-types	0.7	2	2	3	6	16	67	92	100	100	100	0.7	13	7.8	14	8	56
Moyenne Xf	0.6	1	1	2	4	13	61	89	99	100	100	0.6	12	6.0	13	7	56
Xf-1.25xEcart-types	0.4	0	1	1	2	9	55	87	98	100	100	0.4	10	4.2	13	7	55
Minimum	0.4	1	1	1	2	8	52	86	98	100	100	0.4	10	5.0	13	7	55
Ecart-type	0.10	0.5	0.5	1.2	1.7	2.6	4.7	2.2	0.5	0.0	0.0	0.10	1.0	1.40	1.0	1.0	1.0
Nombre de résultats	15	7	15	7	7	15	15	15	15	15	15	15	7	2	4	4	2

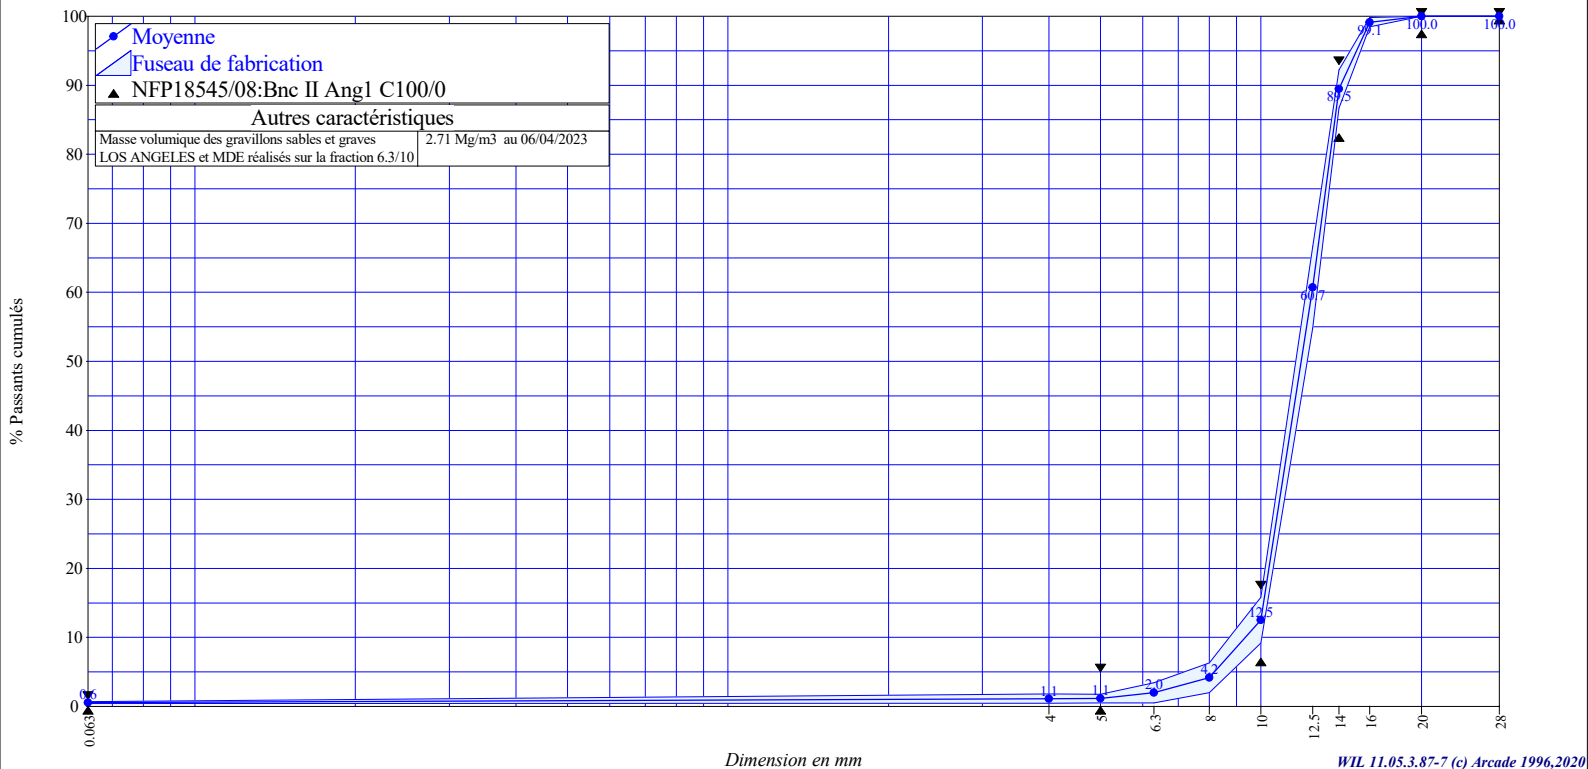

David REYNAL